

# 0/4mm (D3.15)

**Producteur :** Carrière de Sauveterre

**Pétrographie :** Calcaire Barrémien du Crétacé

**Elaboration :** Concassé

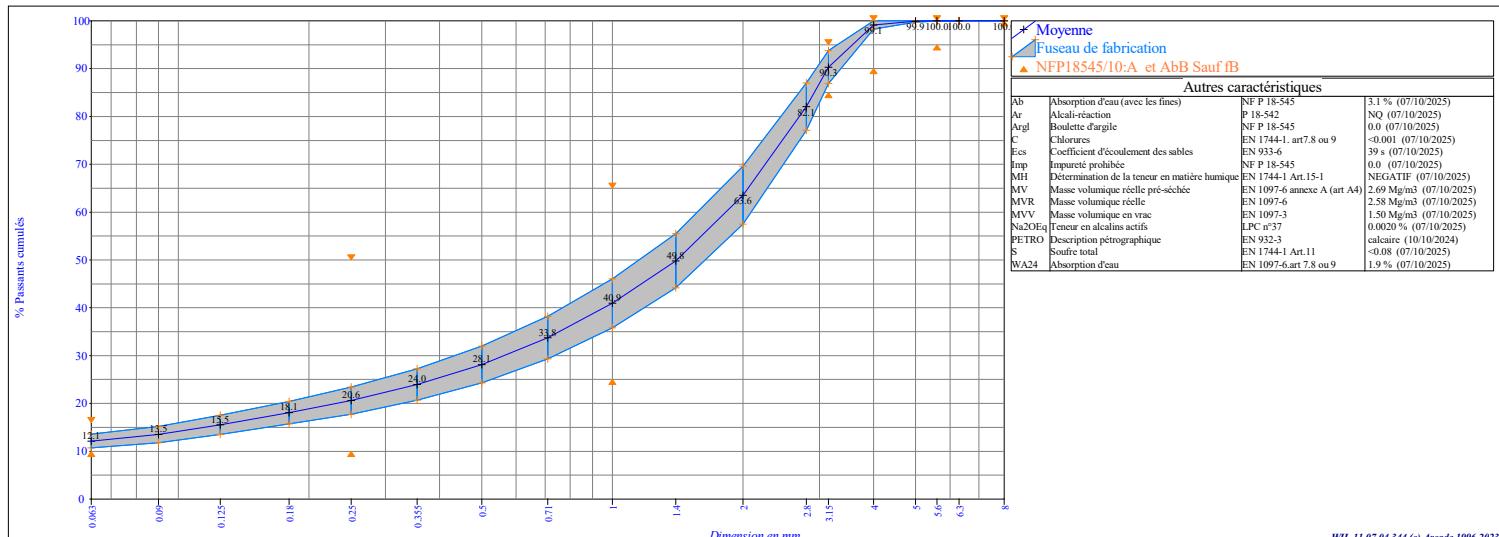
**Partie contractuelle**
*Valeurs spécifiées sur lesquelles le producteur s'engage*
**Classe granulaire**
**Norme**
**Code**
**Norme NF P 18-545 Article 10**

	0.063	0.125	0.25	0.5	1	2	3.15	4	5	5.6	8	f	FM	MB
Etendue e	6		40		40			10				6	0.6	
V.S.S.+U	18.0		54		69			100				18.0	3.75	2.0
V.S.S.	16.0		50		65			95	100			16.0	3.60	1.5
V.S.I.	10.0		10		25			85	90		95	100	10.0	3.00
V.S.I.-U	8.0		6		21			88			94		8.0	2.85

**Partie informative**  
*Résultats de production*

du 15/07/25 au 08/12/25

	0.063	0.125	0.25	0.5	1	2	3.15	4	5	5.6	8	f	FM	MB
Maximum	13.3	17	24	33	47	71	94	100	100	100	100	13.3	3.60	1.4
Xf+1.25xEcart-types	13.6	18	23	32	46	70	94	100	100	100	100	13.5	3.52	1.4
Moyenne Xf	12.1	16	21	28	41	64	90	99	100	100	100	12.1	3.32	1.1
Xf-1.25xEcart-types	10.7	13	18	24	36	57	87	98	100	100	100	10.7	3.13	0.9
Minimum	10.0	12	16	22	33	57	85	97	99	100	100	10.0	3.09	0.9
Ecart-type	1.15	1.6	2.3	3.1	4.1	4.9	2.8	0.7	0.2	0.0	0.0	1.10	0.150	0.20
Nombre de résultats	15	15	15	15	15	15	15	15	15	15	15	15	15	15


**F. CARLETTI**
